

Compound

**23711****ETHYLENE PROPYLENE  
70 DUROMETER - BLACK COLOR  
ALKALI/ACID RESISTANT****PRODUCT DATA SHEET**

Compound 23711 is a 70 durometer black colored high strength EPDM rubber formulated specifically for use in alkalis and acids, with the exception of concentrated sulfuric and nitric acid. It exhibits good resistance to heat and compression set. This, coupled with its good low temperature flexibility, allows for its use over a wide temperature range. Compound 23711 is also very resistant to polar materials such as water, phosphate esters, ketones and alcohols. The phosphate ester resistance makes it very useful for automotive brake fluid applications. Further, it demonstrates excellent resistance to weathering and steam. It is also a peroxide cured compound.


This compound will meet or exceed the specifications listed and has the following physical properties:

ASTM D2000	2 AA 720 A13 C12 EA14 F17 EA14
	3 AA 720 B13 B33 C12 F17 EA14
	4 AA 720 A13 B13 B33 C12 F17 EA14
	5 AA 720 A13 B13 B33 C12 F17 EA14
	2 BA 720 C12 F17
	3 BA 720 A14 B13 C12 F17 F19
	4 BA 720 A14 C12 F17
	5 BA 720 F17 F19 C12
	6 BA 720 B13 C12
	3 CA 710 A25 B44 B35 EA14 C32 F17 F18 F19 G11 G21
	4 CA 720 A25 B35 EA14 C32 F17 F18 F19 G11 G21
	5 CA 720 A25 B35 EA14 C32 G11 G21
	2 DA 720 A26 B36 C32 EA14 F19 G11 G21
	3 DA 720 A26 C32 EA14 F19 G11 G21

Compound 23711 is UL approved per JOHX2 for water, steam, air and inert gasses. This compound is also suitable for use in anhydrous ammonia.

**Original Properties**

Modulus @ 100% Elongation	371 psi	2.6 MPa
Tensile Strength	2478 psi	17.1 MPa
Ultimate Elongation	351 %	
Hardness, Shore A	72 Durometer	
Specific Gravity	1.10 grams/cc	
Brittleness Temperature	< -89 °F	< -67 °C
Tear Resistance, Die B	207 ppi	36.3 kN/m
Tear Resistance, Die C	210 ppi	36.8 kN/m

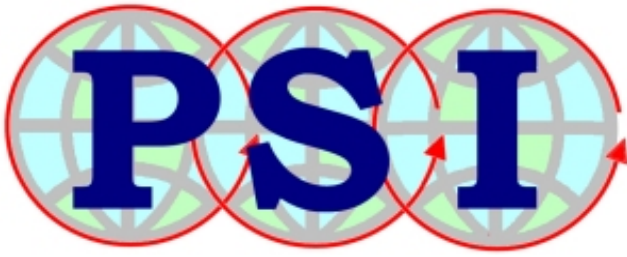

Compound

**23711**ETHYLENE PROPYLENE  
70 DUROMETER - BLACK COLOR  
ALKALI/ACID RESISTANT**PRODUCT DATA SHEET****TEST DATA ONLY - DO NOT USE FOR SPECIFICATION****Compression Set**

Solid: 22 hrs @ 158°F (70°C)	11.2 %
Solid: 22 hrs @ 212°F (100°C)	10.2 %
Solid: 22 hrs @ 257°F (125°C)	13.3 %
Solid: 22 hrs @ 302°F (150°C)	24.2 %
Solid: 70 hrs @ 212°F (100°C)	15.2 %
Plied: 22 hrs @ 158°F (70°C)	12.2 %
Plied: 22 hrs @ 212°F (100°C)	12.1 %
Plied: 22 hrs @ 257°F (125°C)	18.5 %
Plied: 22 hrs @ 302°F (150°C)	44.0 %
Plied: 70 hrs @ 212°F (100°C)	17.4 %

**HEAT AGED: 70 hrs @ 158°F (70°C)**

Change - Tensile Strength	+ 3.0 %
Change - Elongation	+ 2.8 %
Change - Hardness, Shore A	0

**HEAT AGED: 70 hrs @ 212°F (100°C)**

Change - Tensile Strength	- 6.6 %
Change - Elongation	- 7.1 %
Change - Hardness, Shore A	0

**HEAT AGED: 70 hrs @ 257°F (125°C)**

Change - Tensile Strength	+ 3.6 %
Change - Elongation	+ 5.4 %
Change - Hardness, Shore A	+ 1

**HEAT AGED: 70 hrs @ 302°F (150°C)**


Change - Tensile Strength	+ 4.1 %
Change - Elongation	- 5.7 %
Change - Hardness, Shore A	+ 4

**HEAT AGED: 70 hrs @ 257°F (125°C) Test Tube Method**

Change - Tensile Strength	+ 3.6 %
Change - Elongation	- 5.4 %
Change - Hardness, Shore A	+ 1

**HEAT AGED: 70 hrs @ 302°F (150°C) Test Tube Method**

Change - Tensile Strength	+ 4.1 %
Change - Elongation	- 5.7 %
Change - Hardness, Shore A	+ 4



Compound

**23711**ETHYLENE PROPYLENE  
70 DUROMETER - BLACK COLOR  
ALKALI/ACID RESISTANT**PRODUCT DATA SHEET****DISTILLED WATER AGED: 70 hrs @ 212°F (100°C)**

Change - Tensile Strength	+ 15.1 %
Change - Elongation	+ 1.7 %
Change - Hardness, Shore A	0
Change - Volume	+ 0.3 %

**DOT #3 BRAKE FLUID: AGED 300 hrs @ 248°C (120°F)**

Change - Hardness, Shore A	- 3
Change - Volume	- 1.0 %

**DOT #3 BRAKE FLUID: Aged 70 hrs @ 248°F (120°C)**

Change - Tensile Strength	+ 4.8 %
Change - Elongation	+ 0.9 %
Change - Hardness, Shore A	- 2
Change - Volume	+ 0.3 %

**DOT #4 BRAKE FLUID: Aged 70 hrs @ 248°F (120°C)**

Change - Tensile Strength	+ 0.4 %
Change - Elongation	- 4.8 %
Change - Hardness, Shore A	- 3
Change - Volume	+ 2.1 %

**DOT #4 BRAKE FLUID: AGED 300 hrs @ 248°C (120°F)**

Change - Hardness, Shore A	- 2
Change - Volume	- 1.3 %

**DOT #5 BRAKE FLUID: Aged 70 HRS @ 248°F (120°C)**


Change - Tensile Strength	- 4.6 %
Change - Elongation	- 4.8 %
Change - Hardness, Shore A	- 3
Change - Volume	+ 2.1 %

**DOT #5 BRAKE FLUID: AGED 300 hrs @ 248°C (120°F)**

Change - Hardness, Shore A	- 3
Change - Volume	+ 1.0 %

**SAE COMPATABILITY FLUID: 70 hrs @ 248°F (120°C)**

Change - Tensile Strength	+ 6.1 %
Change - Elongation	- 0.6 %
Change - Hardness, Shore A	- 2
Change - Volume	- 0.2 %

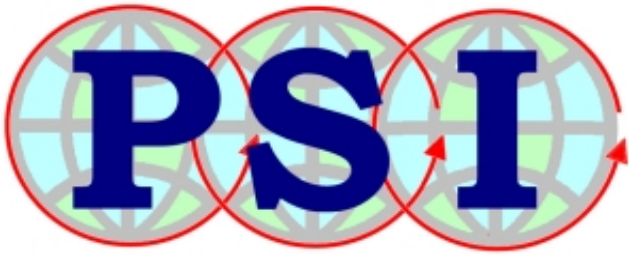

Compound

**23711**ETHYLENE PROPYLENE  
70 DUROMETER - BLACK COLOR  
ALKALI/ACID RESISTANT**PRODUCT DATA SHEET****SAE COMPATABILITY FLUID: 300 hrs @ 248°C ( 120°F)**

Change - Hardness, Shore A	- 2
Change - Volume	- 0.2 %

**50% ETHYLENE GLYCOL/50% H2O: AGED 70 HRS @ 302°F**

Change - Tensile Strength	+ 7.0 %
Change - Elongation	+ 0.3 %
Change - Hardness, Shore A	0
Change - Volume	- 0.5 %

**ETHYLENE GLYCOL: 70 hrs @ 302°F (150°C)**

Change - Tensile Strength	+ 20.4 %
Change - Elongation	+ 5.7 %
Change - Hardness, Shore A	0
Change - Volume	- 0.8 %

**HYDROCHLORIC ACID: Aged 70 hrs @ RT (70°F, 23°C)**

Change - Tensile Strength	+ 18.8 %
Change - Elongation	+ 8.5 %
Change - Hardness, Shore A	+ 2
Change - Volume	+ 3.0 %

**METHANOL: Aged 70 hrs @ RT ( 73°F, 23°C )**


Change - Tensile Strength	+ 5.6 %
Change - Elongation	+ 7.1 %
Change - Hardness, Shore A	- 2
Change - Volume	+ 0.1 %

**METHYL ETHYL KETONE: Aged 70 hrs @ RT (70°F, 23°C)**

Change - Tensile Strength	- 23.2 %
Change - Elongation	- 12.5 %
Change - Hardness, Shore A	- 8
Change - Volume	+ 11.2 %

**NITRIC ACID: Aged 70 hrs @ RT (70°F, 23°C)**

Change - Tensile Strength	- 9.8 %
Change - Elongation	+ 11.4 %
Change - Hardness, Shore A	- 3
Change - Volume	+ 8.1 %

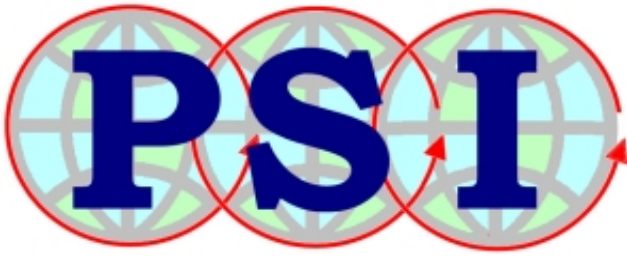

Compound

**23711**

ETHYLENE PROPYLENE  
70 DUROMETER - BLACK COLOR  
ALKALI/ACID RESISTANT

**PRODUCT DATA SHEET**

**SODIUM HYDROXIDE: Aged 70 hrs @ 212°F (100°C)**

Change - Tensile Strength	+ 6.2 %
Change - Elongation	+ 0.3 %
Change - Hardness, Shore A	- 1
Change - Volume	+ 0.1 %

**TR-10 ASTM D1329 (10% Retraction @ °F)**

Temperature	- 48.0 °F
-------------	-----------